Sandia National Laboratories

Zincate-Blocking Polymeric Separators for Zn/MnO_2 Batteries

Igor Kolesnichenko,[1] David Arnot,[1] Matthew Lim,[2] Timothy N. Lambert,[1]* Gautam Yadav,[3] Jungsang Cho,[3] Michael Nyce,[3] Sanjoy Banerjee[3]

[1]Department of Photovoltaics & Materials Technologies, Sandia National Laboratories, Albuquerque, New Mexico 87185, USA

[2]Department of Energy Storage Technology & Systems, Sandia National Laboratories, Albuquerque, New Mexico 87185, USA

[3]Department of Chemical Engineering, The CUNY Energy Institute at the City College of New York, Steinman Hall Room 316, 160 Convent Avenue, New York, New York 10031, USA

***Email:** tnlambe@sandia.gov

Background and Objectives

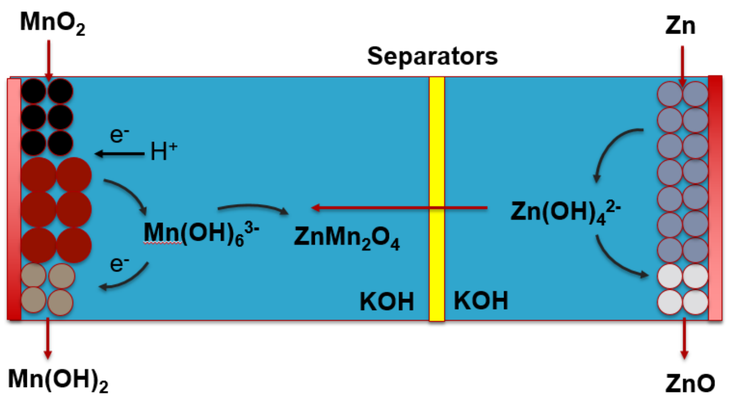

Cathode Failure Mechanisms:

- Formation of irreversible Mn_3O_4.
- Formation of irreversible $ZnMn_2O_4$.
- Passivation from an insulating ZnO layer.

Caused by $Zn(OH)_4^{2-}$ crossover

Objectives:

- Synthesize separators selective for blocking zincate, while allowing for crossover of hydroxide
- Cast membranes with thicknesses similar to those of commercial separators and establish the aforementioned selectivity outside of cells
- Implement into prototype cells and demonstrate an improvement in battery performance

Zinc Diffusion Analysis

Presence of Bi, Cd, and Pb allows for consistent results when determining [Zn]

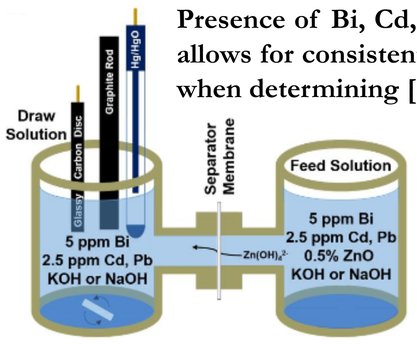

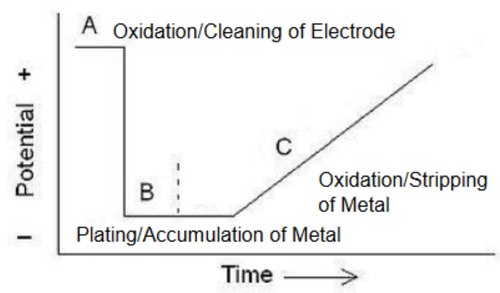

A. J. Bard, L. R. Faulkner, Electrochemical Methods, (2001) 458–466.

Anodic stripping voltammetry (ASV) allows for much faster screening of separators compared to ICP-MS, with similar limits of detection.

ASV Analysis of Zn performed for the first time in alkaline conditions.

J. Duay, T.N. Lambert, R. Aidun, *Electroanalysis,* 29 (2017) 1-8.

Polymeric Separators

Separator	Hydroxide Diffusion Coefficient (cm^2/min) $*10^{-6}$	Zincate Diffusion Coefficient (cm^2/min) $*10^{-6}$	Selectivity	Water Uptake (%)	Thickness (μm)	Conductivity (mS/cm)
Celgard 3501	6.74	5.7	1.18	68	25	12.2
Cellophane 350P00	17.4	2.0	8.70	96	25	13.8
Polymer 1	2.48	0.049	50.6	11	30	5.83
Polymer 2	9.43	0.17	55.5	17	30	7.19
Polymer 3	15.4	0.42	36.7	47	30	8.79
Polymer 4	3.08	≤ 0.000032	10,000	14	25	Approx. 1-4

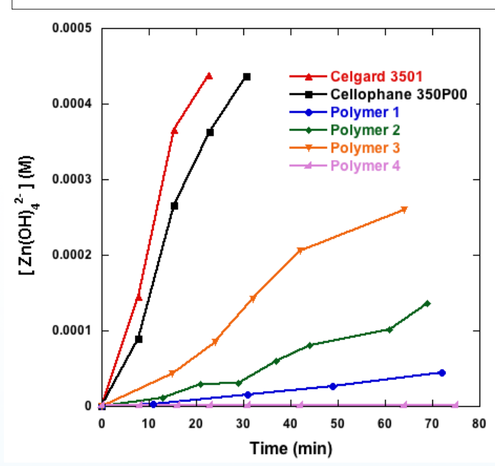

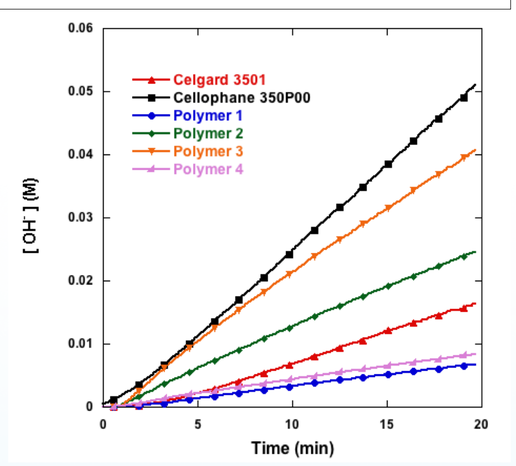

Polymers 1-3 show a greatly improved selectivity ratio over commercial separators for screening out zincate, while allowing for hydroxide crossover. Polymer 4 has an even higher selectivity ratio, but is also far less conductive, resulting in lower practical cycling rates.

Future Goal:

Attain a selectivity ratio on par with Polymer 4, while retaining a conductivity similar to those of commercial separators

Battery Assembly and Cycling

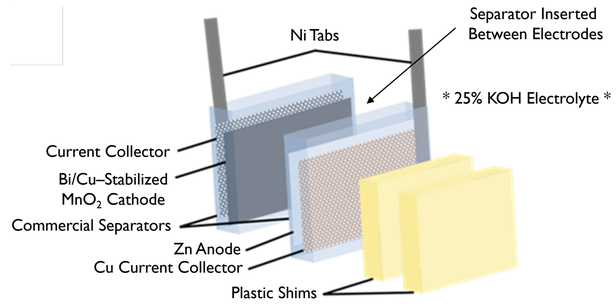

Journal of Power Sources, 395 (**2018**) 430-438

Control cells are assembled by wrapping both the anode and cathode in 3 layers of Cellophane, while the cells containing Polymer 4 are assembled by wrapping only the anode in 3 layers of Cellophane, inserting Polymer 4 between the electrodes (as shown to the left) and using the cathode as received from CUNY, with no additional wrapping.

C/10 Cycling of Cells With and Without Polymer 4

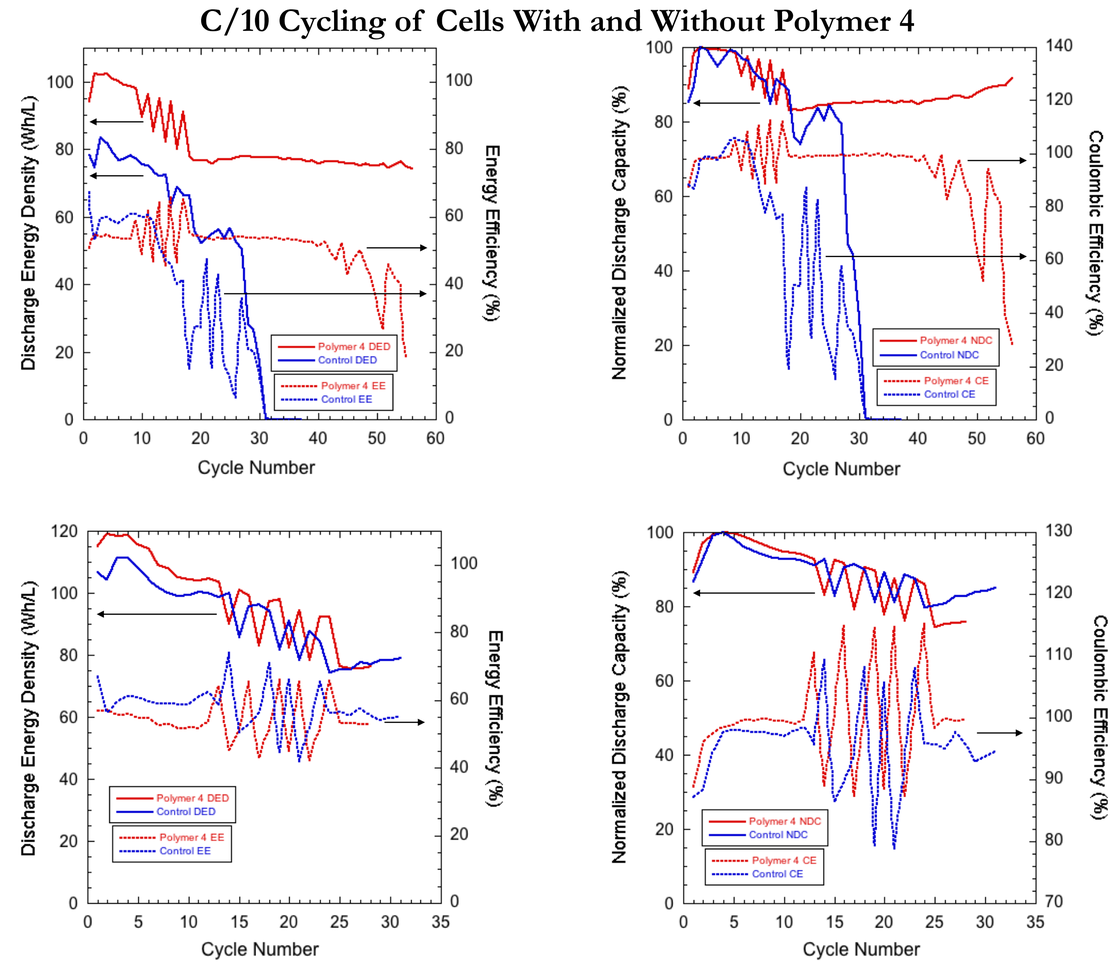

Conclusions and Research Output

- Prepared flexible polymeric membranes that are resistant to zincate, while maintaining hydroxide permeability on par with commercial separators
- Conductivity constraints limit the rates at which functional batteries containing the fabricated separators can be cycled → **Need to improve upon conductivity**
- Preliminary data from Zn–MnO_2 cells shows cycling at C/10 rates that is on par with cells using commercial separators

Publications

- Kolesnichenko, I. V.; Arnot, D. A.; Lim, M. B.; Lambert, T. N. "Zincate–Blocking Functionalized Separators for Secondary Zn/MnO_2 Batteries" *in final preparation*
- Arnot, D. A.; Lim, M. B.; Kolesnichenko, I. V.; Lambert, T. N. "Development of Zincate–Blocking Separators and Their Application in Zinc–Manganese Oxide Batteries" *in preparation*

Acknowledgements

This work was supported by the U.S. Department of Energy, Office of Electricity, and the Laboratory Directed Research and Development program at Sandia National Laboratories. Sandia National Laboratories is a multi-program laboratory managed and operated by National Technology and Engineering Solutions of Sandia, LLC., a wholly owned subsidiary of Honeywell International, Inc., for the U.S. Department of Energy's National Nuclear Security Administration under contract DE-NA-0003525. Department of Energy or the United States Government. Dr. Imre Gyuk, Director of Energy Storage Research, Office of Electricity is thanked for his financial support. The views expressed herein do not necessarily represent the views of the U.S.

U.S. DEPARTMENT OF ENERGY

NNSA National Nuclear Security Administration

Sandia National Laboratories is a multimission laboratory managed and operated by National Technology & Engineering Solutions of Sandia, LLC, a wholly owned subsidiary of Honeywell International Inc., for the U.S. Department of Energy's National Nuclear Security Administration under contract DE-NA0003525.
SAND No. SAND2019-11155 C

Sandia National Laboratories